

Experimental and Simulation Progress on Deep drawing Process

Sanjay K. Ansodariya¹ Bharat J. Kapadiya²

^{1,2}Vadodara Institute of engineering/Mechanical, Vadodara, India

Abstract— Deep drawing is part of forming process in which sheet metal drawn into die cavity by action of a punch. Sheet-metal drawing is a more complex operation than cutting or bending, and more things can go wrong. A blank holding force, punch force, material property of sheet metal, thickness of sheet, velocity of punch, these are all affecting parameters in deep drawing process to regulate wrinkling effect, tearing effect and fracture defect. Nowadays composite material is extensively used in manufacturing industries due to its better strength. Die radius has the greatest influence on the deep drawing of stainless steel blank sheet followed by the blank holder force and the friction coefficient. Further, it is shown that a blank holder force application and local lubrication scheme improved the quality of the formed part.

Key words: Deep Drawing, Parameters, Effects

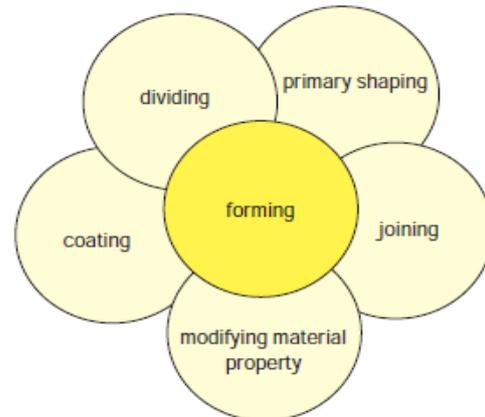


Fig. 1: Manufacturing system. [1]

I. INTRODUCTION

Metal working process has been divided into following given categories such as forming, cutting, and joining. These processes can be used for different purposes depending on the requirement. Before carrying out operations, the work to be done on the metal should be marked out and/or measured depending on required product to be achieved. Marking is process of converting design or pattern to a work piece and it is primary step in metal working. It is done in industries as they need to mark out every piece. In metal treading marking out is transferring engineers' plan to work piece for preparation of next step which may be machining or manufacturing. Thus metal working is basically process of marking, planning and manufacturing by using various manufacturing process. [1]

Manufacturing process is basically classified in to six main categories which are mention below. [1]

- 1) Primary shaping is process of creating of initial shape from molten, gaseous or formless solid state.
- 2) Material forming
- 3) Dividing is process of separation of local material
- 4) Joining is process of assembling individual work piece so that sub-assemblies are created.
- 5) Modify material property is process of altering material characteristics of work piece for achieving certain useful properties such as heat treatment process which includes hardening or recrystallization annealing.
- 6) Coating is process of applying thin layer on components.

A. Metal Forming Process:

In today's era continuous rolling mills are producing bulk quantity of thin sheet metal at low price. Huge amount of all metals are produced a shot rolled striped or cold rolled sheet. Secondary process is done in automobiles, domestic application, building products, aircraft, drink cans. Sheet metals possess advantage for the material having high elastic modulus and yield strength. So, that the parts obtain can have good stiffness and excellent strength to weight ratio. In sheet metal working process the cross section of workpiece does not change but material is only subjected to change in shape the ratio of cross section area to volume is more. [2]

B. Important Process Parameters of Metal Forming Process:

Metal forming process must be done economically so, that the cost is reduced. The important parameters for metal forming process which influence the result of production process is to get the optimum result. The work piece plays an important role which provides sufficient formability which allows required amount of plastic deformation which is without cracks or defects. The main things measured in workpiece are stress, strain; flow stress and temperature that material will be given. [3].

II. DEEP DRAWING PROCESS

Within 2001, few research were done on deep drawing, this process has been studied intensively by several experiment and investigations. To overcome difficulties of deep drawing process very thin metal foils were used as new concept. Required shape and dimensional accuracy were achieved by using auxiliary metal punch together with polyurethane ring. Another approach use of hot isostatic pressing to form micro channels from ultra-thin foils. Mechanical micro deep drawing process is compared with new laser deep drawing process through which shock waves are produced. Lubrication is most important as the sheet slide between die and blank holder. Deep drawing has been carried out with the help of die, blank holder, punch and sheet metal which is show in below. [2]

A. Geometric Parameters Of Deep Drawing Process:

Drawing is sheet metal forming operation used to make cup shaped, box shaped, and complex curved and concave cup. The common parts made by deep drawing process are beverage cans, ammunition shells, sinks, coking ports and automobile body parts. The sheet of metal is formed into 3-D product by deep drawing process. The main tools used in deep drawing process are blank, punch, die and blank holder. The geometry parameters used in deep drawing process are mentioned below. [4]

- Punch Radius (R_p)
- Punch Edge Radius (r_p)
- Blank Thickness (t)
- Blank Radius (R_b)
- Die Radius (R_d)
- Die Edge Radius (r_d)

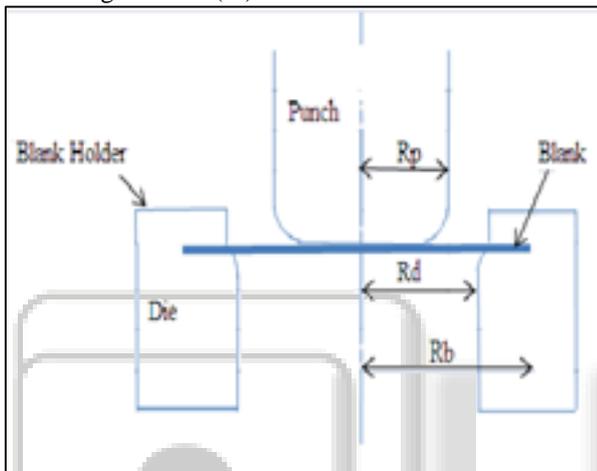


Fig. 2: Tool geometry parameter of deep drawing process. [4]

The geometry parameters must be selected carefully because the final product depends highly on above mention geometries. Clearance is the important parameters which is obtain by the difference between die radius and punch radius ($c = R_d - R_p$). Clearance must be 25% larger than initial blank thickness.

B. Physical Parameters Of Deep Drawing Process:

Physical properties of deep drawing process plays vital role in achieving high accuracy for the final product. Deep drawing process depends on type of blank material, blank holder force, punch speed, die edge radius (r_d), lubrication and drawn depth. Blank holder force mainly produces effect on failure on sheet metal. [4] By reducing BHF wrinkling effect comes as failure and increasing BHF results in splitting and fracture. Die edge radius produces stress concentration which results in tearing effect on the edges of vertical wall of cup. [5] Proper lubrication results in reducing stress, wrinkling and hence results in reducing error in deep drawing process.

C. Defects In Deep Drawing Process:

Deep drawing process is more complicated than cutting or bending because many things can go wrong in deep drawing process which may results in some defects.

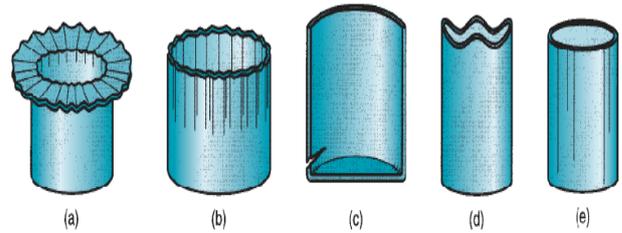


Fig. 3: Defects in deep drawing process.[6]

Figure(a) represents wrinkling in the flange. Wrinkling is mainly cause on flange due to compressive buckling on the undrawn flange.

Figure (b) represents wrinkling on the wall. Wrinkling of wall generally take place in the cup shaped flange.

Figure (c) represents tearing and open crack produced in vertical wall which usually take place near the base of drawn cup thus results in high tensile stress which may lead to thinning and failure of metal at the location shown in the figure(c).Tearing may also occur in metal due to pulling over a sharp die corner.

Figure(d) represents earing. Earing is mainly cause due to forming of irregularities which are called ears and generally occurs on the upper edge of finished part. Earing is also caused by anisotropic in sheet metal. Material must be made up of perfectly isotropic which results in removing of earing.

Figure (e) represents surfaces cratches. Surface scratches mainly occur on the drawn part if the punch and die are not smooth or if the is not done properly.

D. Summary:

Deep drawing process is shape transformation without removing of material. By action of mechanical punch desired shape can achieved. For achieving desired shape of initial blank sheet it must have to control some parameters. If parameters of deep drawing are being taken wrong than various defects are produced which discuss in above point.

III. EFFECTS OF PARAMETERS ON THINNING OF SHEET METAL IN DEEP DRAWING PROCESS

A. Description:

The deep drawing process is very important in the industries which use cold pressure. Sheet metal deformation processes, deep drawing are very complex operation in which the process parameters plays huge role. The processes are punch, die shape, blank shape, blank holder force which acts contact between element and material properties. Prediction of material can be done by decreasing wall thickness of the container and the retaining of container can be done by providing strength for allowing container to serve its purpose without the fear of failure. The objective of the work is to simulate the deep drawing process and the results obtain are validated by making a comparison with literature published previously. The literature contains both experimental and numerical results which are used as benchmark for comparing purpose. The purpose for doing research is that deep drawing process makes manufacturing process efficient by reducing the cost. The use of finite element analysis and statistical method helps in prediction of punch force, blank holder force and the lubrication requirements can be determine through

the thickness of metal. This can gradually reduce the production cost, reduce time for production and provide engineers ability to respond the market changes [5].

B. Tool Geometry Parameter:

Die Radius

In deep drawing process the geometry of die influence the thickness distribution and thinning of sheet metal. Die shoulder radius plays important role in sheet metal thickness distribution. [7]

Punch Radius

The geometry of punch plays important role in the thickness distribution and thinning of sheet metal in deep drawing process. Punch nose radius plays important role in metal thickness distribution. When punch nose radius is less than three times thickness of blank the cup fails and when punch nose radius is greater than three time thickness of blank, thinning is stable. [7]

Sheet Thickness

The original blank thickness plays vital role in thickness distribution and thinning of sheet metal deep drawing process. The average distribution of blank thickness improves with increase in blank thickness. Also the percentage of thinning increases with increase of blank thickness. The blank thickness and punch diameter affect the limiting drawing ratio and limiting drawing ration decrease as the relative punch diameter increases. Thicker material can be gripped properly as diameter increases. Thicker sheets have more volume so it can be stretched greater extend with increasing. [7]

Radial clearance

Radial clearance is difference between die radius and punch radius. Sheet metal thickness increase when radial clearance decreases. When radial clearance is less than blank thickness the cup fails due to increase in thinning. When the radial clearance is greater than blank thickness thinning is stable. [7]

C. Physical Parameter:

Blank holder force

BHF is required to hold a blank which is one third of drawing pressure. The process is limited by strain produce in the side wall. When tension reaches maximum value the side wall will fail by splitting. Cup collapse due to thinning with increase in blank holder force over 0.5 ton. [7].

Cracking Load

The largest allowable drawing load is limited by the load that can be transmitted by the sheet in the region of the punch radius or at the conversion form cup wall to bottom radius, which is known as cracking load. It must always be larger than the maximum drawing load. [8].

Friction parameter

Friction is one of the important parameter in deep drawing process. Friction determines the punch force and blank holder force in case of deformation of sheet. Friction use energy which is needed to deform a sheet material. Friction plays vital role to determine stress and strain in the work piece. It is important to control friction between tool and work piece. In deep drawing process hollow bodies from metal blanks using punch, die and blank holder. In deep drawing process lubrication and friction is complex as compare to other process. In one operation low friction is

required in one area and high friction is required in other area [9].

D. Summary:

The quality of drawn part depends on forming conditions and the parameter considered in deep drawing process. The coefficient of friction increase so the blank holder force will have more importance. Successful deep drawing process depends on geometrical parameters and physical parameters. Deep drawing process is exact method to find desired shape with material deformation.

IV. EXPERIMENTAL WORKS

A. Preliminary Test:

Brass is wide decorative applications and its thermal and electrical conductivities are much better and its specific heat is considerably less higher, compared with those of the stainless steel. Therefore, by making a parts made of brass and stainless steel, one can take different advantages of these metals at the identical time. [10]

In the practical experiments, it is firstly necessary to find the mechanical properties of the selected materials as well as the Coulomb friction co-efficient between the sheet and the dies. These data are also required for performing the FE simulations of the process. For this case, the tensile tests, based on ASTM (E8M-98) standard, were used to specify the stress-strain curves of the brass and stainless steel under consideration. This type of test is usually adopted for sheet metal forming processes, because of the stress state involved. For more precise evaluation of strain, all the tensile tests were conducted using an extensometer. The thicknesses of the steel and brass sheets were 0.39 and 0.62 mm, respectively to meet enough clearance between the punch and die. [11]. Fig. 6 represents schematically the fixture used for evaluation of the friction coefficients. For each frictional condition, a normal force (N) was applied to the sheet by the press and, then, the horizontal force (F) needed for initiation of motion of the sheet between the die faces was measured. Afterwards, using the Coulomb friction formula, the friction coefficient was calculated. Three different frictional conditions were tried for both the steel and brass sheets.

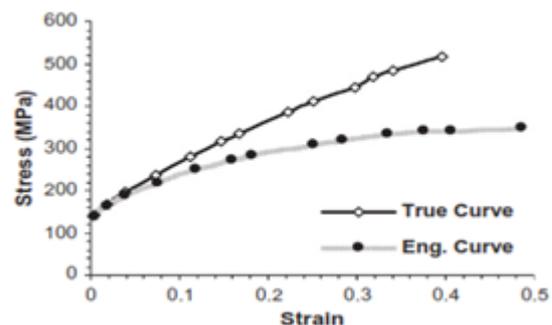


Fig. 4: Engineering Stress vs. Strain Diagram. [10]

B. Deep Drawing Test:

The process variables selected for investigation were the layer stacking sequence, blank diameter, blank-holder force and lubrication. Therefore, blanks with three diameters 7.5, 8.5 and 10 cm from stainless steel and brass sheets were punched to make composite sheets.

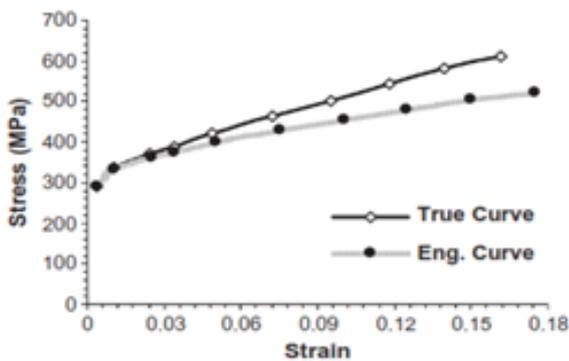


Fig. 5: Stainless steel Diagram [10]

Lubrication with nylon film and dry condition were also two different contact conditions maintained between laminated sheet and punch, die and blank-holder. The blank holder force was adopted with three levels, namely 0.71, 2.14 and 3.56 KN. These values were selected considering the guidelines suggested by Johnson and Mellor. [10] The blank holder force was exerted by means of eight B-16/76 standard springs. This force was kept constant during each drawing experiment. It is helpful to note that recommended blank-holder force to have defect-less products must obey Equations. Dry condition and nylon sheet as a lubricant were considered for tool workpiece interface. The stacking sequence involved two cases, namely BS and SB. In BS case, the stainless steel layer was in contact with the punch and the brass sheet was positioned underneath. In SB state, there was a reverse situation, i.e. the brass material layer in case of the composite blank contact with the help of punch. [10]

C. Summary:

In experimental work the first step is primary test of material properties of various materials (brass and stainless steel) and gets stress vs. strain curve for these materials. From the curve we can say that stainless steel having higher values of parameter. The second step is deep drawing test in which some important parameters are selected like blank diameter, blank holder force, and lubrication and other and test will be done in two ways SB and BS in which we get different result.

V. SIMULATION TECHNIQUES

The first sandwich material to be used in industry was in 1994, wood sandwich material consists of plywood and balsa which was used in air craft there was rapid development in aircraft industry whose demand was light, stiff, and strong material which led to wide spread development of different sandwich material. In 1987 and advance sandwich material to known as GLARE (Glass laminate aluminum reinforce epoxy). This sandwich material offers better damage tolerance, excellent corrosion and fire resistance with reduction of weight. [12]

Earlier research work on the optimization in deep drawing used simple rule-of-thumb optimization techniques that play on less rigorous mathematical and analytical tools. The reason for that is due to the convolutedness of the mathematical models that describe the deep drawing process. The work of Conry et al(1980) is a good example for that. They work out a nonlinear mathematical programming model to determine the unsurpassed die profile. This model turned to be very stubborn and complex to be solved mathematically. They evolved an iterative optimization approach combining

regression curve fitting and the techniques for constrained optimization. Nevertheless, since there is no experimental or simulation verification of this study, there is no pledge for its realistic pertinence. [13]

So, the Finite element (FE) simulation and analysis gives a fertile environment for improvement and optimization in deep drawing. To overcome the unconvinced in the mathematical models of the deep drawing process, some researchers worked on developing empirical formulas that are based on the FE simulation results. Such empirical formulas are simple to deal with using a suitable optimization algorithm. [13]

The inverse approach is developed for sheet metal forming processes and it is a simplified efficient finite element method. It is based on the idea of estimating the large plastic strains in thin metallic plates. It is mainly express the knowledge of the 3D shape of the final work piece, and used to find the original position of each material point in the flat blank after that it is possible to estimate the strains and stresses in the final work piece. [13]

A. Simulation Procedure for Deep Drawing Process. [14]:

First of all 2D model is created and give the material properties which selected for testing than load will applied as per experimental test and then check the results. This simulation work follows following steps

Preprocessing: defining the problem;

- Define key points/lines/Areas/volumes (Solid Modeling)
- Define element type and material/geometric properties
- Mesh lines/areas/volumes as required
- Solution: assigning loads, constraints and solving;
- Apply the loads
- Specify constraints (translational and rotational)
- Post processing: further processing and viewing of the results;
- Lists of nodal displacements and show the deformation
- Element forces and moments
- Stress/strain contour diagrams

Solid Modeling

The process of creating solid model in CAD system. A solid model is defined by volumes, areas, lines, and key points. By using various geometrical data of presented setup a solid modeling of the same is created in ANSYS. Solid modeling of the experimental set up is done by using various dimension of the geometry. [15]

Elements

The type of element to be used in the analysis influences the exactness and accuracy of the results to a great extent. Literature review and examination of peer researchers' works show that PLANE42, 2-D elements with axis symmetric behavior have been conveniently used in the numerical analysis of axis symmetric forming process. [15]

Material Properties

The material of back plates is mild steel IS 2062 grade. It was selected as a structural, non-linear, isotropic hardening material model in the presented ANSYS simulation. Various material properties like yield stress, Modulus of elasticity, Poisson's ratio etc, which are required for fem simulation are obtained from various authentic literature. Tools are assumed as rigid, so there is no need to define material, however the material of punch and die is tool steel. [15]

ANSYS meshing

A quad mapped mesh was generated on all areas apart from the punch/die which is taken as rigid. This was done to achieve a higher number of elements along this line so a solution using contact conditions could be found easier. [15]

Loading and boundary condition

As part of FE analysis, applying loads and constraints i.e. boundary conditions consists of defining which parts from geometrical model moves i.e. defining degree of freedom. Contact surfaces used in the presented work are top blank - bottom punch, bottom blank - top die. In current study movement of blank part is restricted in x-direction. Displacement load of the part of the blank which initially not in contact with die is given in y-direction. Movement of horizontal part of the blank which is on the die is restricted in x- direction as well as in y-direction both. The tools i. e. punch, die and blank holder, in finite element simulation are considered rigid because they are extreme stiff compared to the sheet. For this reason the tool can be presented as a surface only. [15]

Finite Element simulation model

Author Amir Atrian has presented result of simulation by finite element method and it is show in Figure-7 In which they have for each frictional condition, the average value of the friction coefficients obtained for brass and steel were used as the friction coefficient between the steel and brass layers. All parts of the die set were modeled rigid to reduce calculation time. Figure-7 illustrates the deformed finite element model in ANSYS.

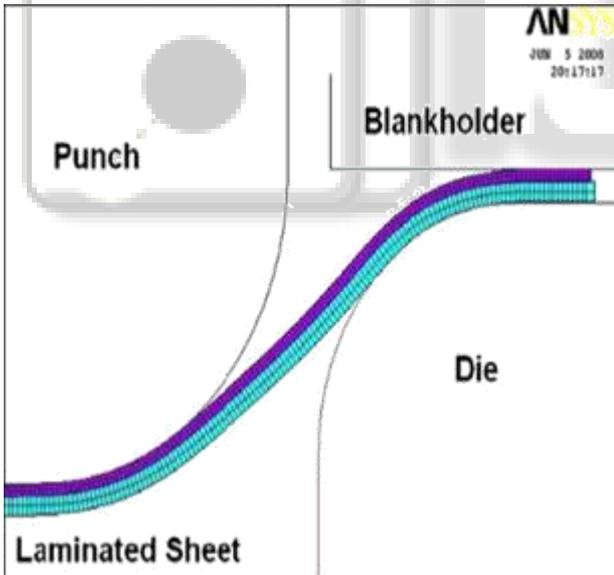


Fig. 7: 2D Finite-element modeling of the deep drawing of composite sheets.

Results of FEM. [10]

The effects of all the variables on the load–displacement curve are presented and discussed in this section. Fig. 8 typically compares the load–displacement curves obtained from two different solutions. This figure illustrates that FE results usually predict a greater forming load for doing the operation. This overestimation of the FE solution is about 10% and more or less is observed in other comparisons between the experimental and finite element results. Therefore, selection of the forming machine capacity

based on the FE results includes a safety factor for having a successful operation.

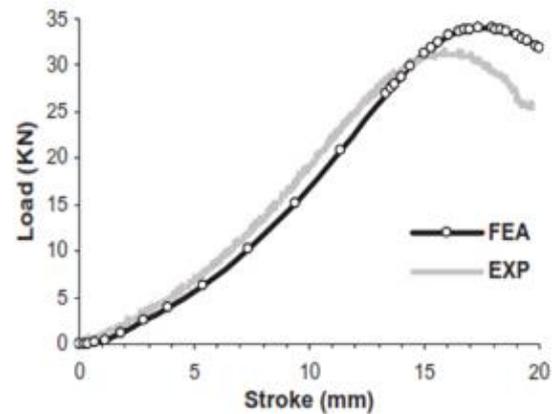


Fig. 8: A typical comparison of experimental and finite element load–displacement curves.

In the composite sheet behavior in a forming process differs from single-layer sheets and depends on the layer sequence and thicknesses. Despite the effect of friction, the early part of the curve is also changed, as can be seen in Fig. 8. It was also observed that the friction condition can change the influence of the stacking sequence.

As an example, for dry condition, when the steel layer was in contact with the punch (BS), the maximum load was about 7% greater than the similar situation with SB case. But when nylon sheet was employed as lubricant, the SB condition needed nearly 14% greater force, compared with the BS case under similar conditions. These observations are almost confirmed by the FE finding. Under the dry condition, when the steel layer was in contact with the punch (BS), FE results showed that a greater force, about 1.5%, was needed compared with the other arrangements. However, with nylon lubricant, 8.5% greater force was required for the SB stacking sequence.

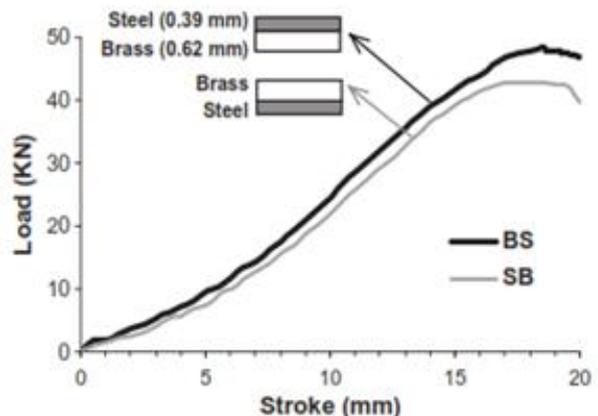


Fig. 9: Effect of layer stacking sequence on the load–displacement curve for dry condition



Fig. 10: The effect of decreasing the blank holder force (from left to right) on occurrence of wrinkling at the edges of composite blanks. behavior of finished part.

For deep drawing of composite blanks, the selection of appropriate blank holder force is also critical. Its good combination between experimental and finite element result which is show that Finite element method can be used in various industrial process. Sequence of layer is also important on the .By changing the order of layer various defects can be observed in the deep drawing process of bi-metallic strip. Circumferential stress and thickness strain produced in drawn cup in the region of punch radius area which is most critical area for the drawn cup. From that point it is more chance to fracture and splitting.

VI. CONCLUSION

It has reviewed that in manufacturing world forming process is most concerning process. Forming is process through which desired shape can be achieved without metal removing. In forming process a deep drawing process has been covered. So, this paper deals with the various parameters of deep drawing process which plays major role to obtain the finish part as well as optimization technique to improve the productivity and quality of product. Lubrication is also plays effective role in fine deep drawing process. By using lubrication in deep process wrinkling effect is firmly reduced. In recent years composite material is widely used in aerospace, auto motive and utensil industries which are stated in paper.

REFERENCES

- [1] Amir Atrian an. el.; "Deep drawing process of steel/brass laminated sheets"; international journal of Composites: Part B; 47 (2013) 75–81.
- [2] J. Jeswiet an.el. "Metal forming progress since 2000"; CIRP Journal of Manufacturing Science and Technology; 1 (2008) 2–17.
- [3] Henry S. Valberg an. el.; "Applied Metal Forming including FEM Analysis"; 1st edition; Cambridge University Press; 2010; ISBN- 978-0-521-5183-9.
- [4] Serhat Yalcin an. el; "Analysis And Modeling Of Plastic Wrinkling In Deep Drawing"; Master Of Science Dissertation; Dept. Mechanical engineering; Middle East Technical University; Turkey.
- [5] Mohammad Reza Morovvati an. el.; "Experimental and finite element investigation on wrinkling of circular single layer and two-layer sheet metals in deep drawing process"; International Journal of Advance

- Manufacturing Technology; volume-54 (2011); pp-113-121.
- [6] Mikell P. Groover; ed "Fundamentals Of Modern Manufacturing"; Materials, Processes, and Systems; 4th edition; John Wiley & Sons, Inc; 2010; ISBN 978-0470-467002.
- [7] M. El Sherbiny an. el; "Thinning and residual stresses of sheet metal in the deep drawing process"; Materials and Design 55 (2014) 869–879.
- [8] Kakandikar G.M an. el.; "Optimization of forming load and variables in deep drawing process for automotive cup using Genetic Algorithm"; On-line Journal, www.optimizationonline.org/DB_FILE/2007/03/1606.pdf.
- [9] Ter verkrijging van; "Modelling of contact and friction in deep drawing Processes"; Printed by FEBO druk B.V., Enschede; Printed by FEBO druk B.V., Enschede
- [10] Amir Atrian an. el., "Deep drawing process of steel/brass laminated sheets"; international journal of Composites: Part B 47 (2013) 75–81.
- [11] Johnson W an. el., "Engineering plasticity"; John Wiley & Sons; 1983.
- [12] O.A. Sokolova an. el., "Deep drawing properties of lightweight steel/polymer/steel sandwich composites"; archives of civil and mechanical engineering; 12 (2012) 105–112.
- [13] Conry, T. F. an. el., "Optimization of die profiles for deep drawing", Journal of mechanical design, Vol. 102, no. 3, pp. 452-459.
- [14] Abdalla S. Wifi, "A review of the optimization techniques applied to the deep drawing process" International Conference on Computers and Industrial Engineering, October 20-23, 2007, Alexandria, Egypt, edited by M. H. Elwany, A. B. Eltawil.
- [15] Yusofi M, an. el., "Theoretical and experimental analysis of stress and strain in deep drawing process" ; Proceedings of the 5th Iranian conference of manufacturing engineering; Tehran, Iran, Conference, Conference; 2002.
- [16] Fereshteh-Saniee F, an. el., "A comparative estimation of the forming load in the deep drawing process"; J Mater Process Technology 2003; 140(1–3):555–61.
- [17] Zein H et al., "Thinning and spring back prediction of sheet metal in the deep drawing process", J Mater Des 2014; 53(2014):797–808.
- [18] Fereshteh-Saniee F, an. el., "A comparative estimation of the forming load in the deep drawing process"; J Mater Process Technol 2003; 140:555–61.
- [19] Danckert J, an. el.; "The residual stress distribution in the wall of a deep drawing and ironed cup determined experimentally and by finite element method" Ann CIRP 1994; 43:249-52.
- [20] Brabie G, an. el. "Analysis of the stresses distribution in the case of drawn parts made from metal sheets"; Int conf INETFORSMEP; Poznan; 2008. p. 86–90.
- [21] M. Kleiner, M. Geiger, A. Klaus; "Manufacturing of Lightweight Components by Metal Forming"; CIRP annals; Manufacturing technology, volume-52 issue-2; 2003; pp- 521-542.
- [22] Jyhwen Wang, an. el.; "Blank optimization for sheet metal forming using multi-step finite element simulations"; International Journal Advance

Manufacturing Technology; volume-40 (2009); pp-709-720.

- [23] T. S. Yang, an. el.; "The design of blank's initial shape in the near net-shape deep drawing of square cup"; Journal of Mechanical Science and Technology; volume-21 (2007); pp-1585-1592.
- [24] Z. Marciniak, J.L. Duncan, S.J. Hu; ed "A Mechanics of Metal Forming"; 2nd edition; Butterworth-Heinemann; imprint of Elsevier science; 2002; ISBN- 0-7506 -5300-0.

