

An Experimental Study on Strength Properties of Hybrid fiber Reinforced Concrete

M Hari Prasad¹ Dr.K.Rajasekhar² C.Sreenivasulu³

¹P.G.Student ²Professor ³Assistant Professor

^{1,2,3}Department of Civil Engineering

^{1,2}Siddhartha Educational Academy Group of Institutions Integrated Campus, Tirupati (R), JNTUA, A.P

³Annamacharya Institute of Technology and sciences, Tirupati, JNTUA, A.P

Abstract— The present investigation is mainly focused on finding the short term mechanical properties of M20 grade hybrid fiber reinforced concrete (HFRC) mixes with different fibers blending. Crimped steel and chopped mat glass fibers are blended in different proportions (0:0, 0.25:0.25, 0.5:0.5, 0.75:0.75 and 1:1) by percentage of volume of concrete and weight of cement. Coarse aggregates of size 20 mm and 10 mm are blended in 60:40 proportions by percentage of weight of total coarse aggregate. Ordinary Portland cement of grade 53(OPC) was used as a binding material. Compressive strength and splitting tensile strength (STS) were studied after 7, 28 and 90 days of curing period. Impact strength and sorptivity were also studied after 28 and 45 days of curing. From the results, it is revealed that the mechanical properties were increased till fibers blending of 0.75:0.75 and decreasing trend has been observed at 1:1 fibers blending. Impact strength and sorptivity results have shown improvement till the fibers blending of 1:1. It is concluded that optimum fiber blending was 0.75:0.75 by percentage of volume of concrete and weight of cement.

Key words: Hybrid fiber reinforced concrete, crimped steel fiber, chopped mat glass fiber, compressive strength, splitting tensile strength, impact strength, sorptivity

I. INTRODUCTION

In India, the construction industry plays an important role due to the construction of buildings and also for developing infra structures in that the most commonly used material is concrete. The ingredients like cement, coarse aggregates, and fine aggregates along with water are used for the homogenous mix of concrete.

The variations in strength properties of concrete can be achieved by changing the proportions of ingredients like fly ash, ground granulated blast furnace slag and rice husk ash etc are added to the concrete for better strength properties and these ingredients are commonly called as admixtures. Due to its high compressive strength, better durability characteristics along with low construction as well as maintenance cost it has been used in large amounts for various civil engineering applications.

The well-known fact of concrete is very strong in compression but when it comes to the tensile property it is very weak and tends to fail because of its deficiencies such as low tensile strength, low strain at fracture. The weakness of concrete is due to the presence of micro cracks at mortar aggregate interface.

II. FIBRE REINFORCED CONCRETE

A. Fibre Reinforced Concrete

Due to the weakness properties of concrete a special type of concrete has been developed known as Fiber reinforced concrete. In FRC the fibers are added to the concrete mix so that those are discontinuous fibers will be uniformly distributed in the mix. Thus due to the addition of fibers there will be improvement in concrete in all directions. Because of fiber inclusion in the concrete mix fibers acts as crack arrester so that there will be a restriction for the development of cracks. The addition of two or more different fibers in the concrete mix is termed as Hybridization

B. Concept of Hybridization

The different fibers are chosen based on their inherent properties i.e. if two different fibers are added in the mix one fiber should strong and stiff properties whereas the other should possess flexibility and ductility. Thus due to the combination there will be improvement in initial crack stress, ultimate strength and toughness after cracking.

Thus hybridization results in bridging of both micro cracks and macro cracks in the different stages by choosing an appropriate fiber to the concrete mix.

Ranjith Kumar.R[11] has done experiments on strength of concrete by adding steel and glass fibers having different aspect ratios with 2% of weight of cement. They concluded that as the aspect ratio is increased strength properties have been increased and the maximum results are for fibers having aspect ratio 100.

Chandra mouli K.[12] has studied on the addition of glass fibers in concrete. Glass fibers are added at 0.03% of volume of concrete for different grades and concluded that there will be 20 to 25% improvement in compressive strength and 15 to 20% in tensile and flexural strengths due to the addition.

Wakchaure M. R [13] has studied compressive strength and flexural strength by hybridizing with steel and glass fibers and compared with normal concrete.

They concluded that at optimum percentage addition the mix will gain maximum strength

III. EXPERIMENTAL STUDY

Our objective was to determine the optimum percentage of addition of fibers to HFRC and study the strength properties viz. compressive strength, splitting tensile strength, impact strength and sorptivity of HFRC, to analyse the properties after the addition of fibers and comparing that to conventional concrete. The hardened properties that were determined are compressive strength and splitting tensile

strength after 7, 28 and 90 days of curing at room temperature and also impact strength and sorptivity were studied after 28 and 45 days of curing respectively.

Ordinary Portland cement of 53 grade (OPC) having initial and final setting time of 50 min and 270 min respectively and specific gravity of 3.10 was used as a binding material, conforming to IS 12269- 1987 [14]. The normal consistency [15] and soundness [16] of cement are 38% and 7 mm respectively. Crushed granite stones of size 20mm and 10mm are used as coarse aggregate, natural river sand is used as a fine aggregate. As per IS: 2386 (Part III)-1963 [17], the bulk specific gravity in oven dry condition, water absorption and fineness modulus of the coarse aggregate and fine aggregate are presented in Table 1.

Properties	Coarse aggregate		Fine aggregate
	20 mm	10 mm	
Specific Gravity	2.56	2.56	2.7
Water absorption (%)	0.3	0.3	1
Fineness modulus	3.36	1.98	2.58

Table 1: Material properties

In the present investigation crimped steel and chopped mat glass fibers are used to improve the strength properties of hybrid fiber reinforced concrete. The length and diameter of steel fiber are of 25 mm and 0.5 mm. The length of glass fiber is 40-50 mm. The tensile strength of steel and glass fibers are 500-700 MPa and 110 MPa respectively.

Ordinary tap water is used in the investigation during the period of casting as well as curing.

A. Mix design of HFRC

The strength properties of hardened concrete are studied by casting cube and for impact test L/4 of cylinder specimens were casted. For M₂₀ concrete mix proportion specimens were cast and tested after 7, 28 and 90 days of curing. The materials for the mix proportion were calculated as per IS codes [18&19] for grade like M₂₀. In this study, the steel fibers and glass fibers are added in mix with different proportions by volume of concrete and weight of cement in mix. The percentage addition of fibers is presented in Table 2.

Fiber added in concrete mix (%)	Steel Fibers Volume of Concrete (%)	by of	Glass Fibers	
			by of (%)	Weight of Cement
0	0		0	
0.5	0.25		0.25	
1	0.50		0.50	
1.5	0.75		0.75	
2	1		1	

Table 2: Different variations of fibers in the mix

B. Test Specimens

Three cubical and cylindrical specimens of size 150 mm x 150 mm x 150 mm and length 300 mm, 150 mm diameter were cast and tested for each age and each mix for compressive strength and split tensile strength. The compressive and split tensile strength of a HFRC was tested after 7, 28 and 90 days of curing. For impact test L/4 of cylinder i.e., 75 mm of length and diameter of 150 mm specimens were casted and cured for a period of 28 days. In case of sorptivity, the specimens having 150X150mm surface area were casted and cured for a period of 45 days and it is coated with non absorbent material on all sides except on side of contact with the water.

C. Curing of Test Specimens

After casting and demoulding, the test specimens were kept in normal water for curing at room temperature till the execution of the testing on the specimens.

IV. METHODOLOGY

The strength studies on short-term mechanical properties of the hybrid fiber reinforced concrete are evaluated by using Compressive strength test, Splitting tensile test, impact strength and sorptivity. The Compressive strength test [20&21], Splitting tensile test [22&23], impact strength [24] and sorptivity [25&26] of all specimens were evaluated by using respective codes.

V. RESULTS AND DISCUSSIONS

A. HFRC Fresh Properties

Table 3 shows the HFRC fresh properties i.e., slump cone test and compaction factor test. These fresh properties give the workability of the concrete.

Figs. 1 and 2. present the results of fresh properties of HFRC. It shows an addition of fibers in concrete gives decrease in the slump values.

% of fibers	Slump (mm)	Compaction factor
0	94	0.96
0.5	90	0.91
1.0	85	0.89
1.5	83	0.87
2	80	0.85

Table 3: Slump and Compaction factor test results

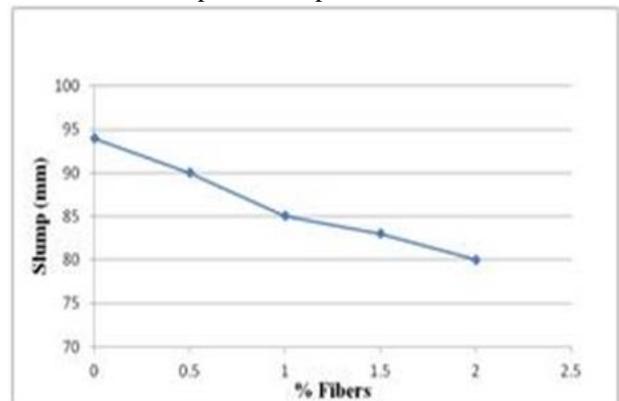


Fig. 1: Slump Test

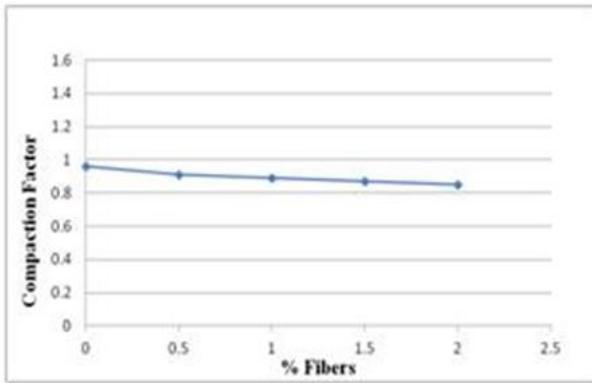


Fig. 2: Compaction factor Test

The reason behind the results is the fibers are added to the concrete, bleeding will be reduced and the mix will become harsh. From this we can conclude that the percentage of fiber content is increased then the workability will be decreased.

It can be observed from Fig 2, the fiber content in the mix increase the compaction factor values will be decreases. From this we can conclude that the workability of the mix decreases as the content of the fiber in the concrete increases.

B. Mechanical Properties

Compressive strength and splitting tensile strength of HFRC were tested on cubes and cylinders with different percentages of steel and glass fibers for M20 grade mix are tabulated. The strength of HFRC has been tested after 7, 28 and 90 days of normal curing.

C. Compressive Strength

Table 4 and Graph:1. shows the compressive strength of HFRC mixes (0%, 0.5%, 1%, 1.5% and 2%) at different curing periods and % variation of compressive strength of HFRC over controlled concrete.

Compressive strength was tested for the mixes with the addition of various percentage of fibers i.e., of 0%, 0.5%, 1%, 1.5% and 2% by volume and weight of cement in concrete. The samples were tested after curing periods of 7, 28 and 90 days.

% of fibers	Age (Days)	Compressive Strength (MPa)	% Variation of compressive Strength of HFRC
0	7	19.542	0
0.5		21.255	8.76
1		23.435	19.92
1.5		24.824	27.02
2		20.332	4.04
0	28	27.596	0
0.5		30.253	9.62
1		31.692	14.84
1.5		32.359	17.25
2		29.324	6.26
0	90	32.254	0
0.5		34.442	6.78
1		35.991	11.58
1.5		37.642	16.7
2		34.224	6.1

Table 4: Compressive strength of HFRC

It was observed that there was a significant increase in compressive strength with the increase in percentage of fibers from 0% to 1.5% in all curing periods. After 7 days of curing, 1.5% fibers sample exhibited a compressive strength of 24.82 MPa, whereas after 28 days of curing it was 32.35 MPa and after 90 days of curing it was 37.64 MPa.

It is to be noted that the significant improvement in compressive strength is mainly due to the addition of fibers in concrete. From the results it is concluded that the fibers blending will enhance the initial crack stress, ultimate strength and toughness after cracking. Thus hybridization results in bridging of both micro cracks and macro cracks in the different stages by choosing an appropriate fiber to the concrete mix gives the best results. However, when the percentage fibers were increased to 2% a drastic fall in compressive strength was evidenced irrespective of the time of curing. The compressive strength values of the mixes with 2% addition of fibers were found to be 20.33 MPa, 29.32 MPa and 34.22 MPa respectively after 7, 28 and 90 days of curing.

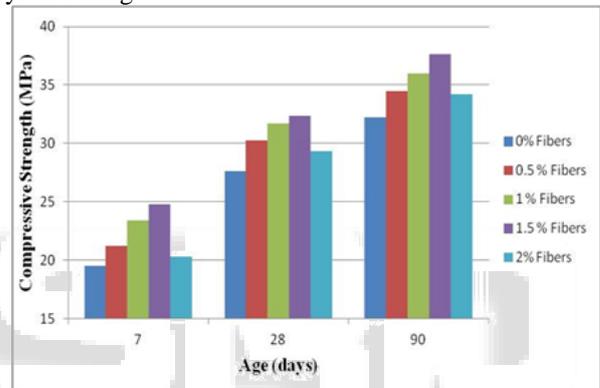


Fig. 3: Compressive Strength (MPa) vs Age

D. Split Tensile Strength

Table 5 and Graph 2. shows the split tensile strength of HFRC mixes (0%, 0.5%, 1%, 1.5% and 2%) at different curing periods and % variation split tensile strength of HFRC over controlled concrete.

% of Fibers	Age (days)	Split tensile strength (MPa)	% Variation of split tensile strength of HFRC over Controlled
0	7	2.59	0
0.5		2.74	5.79
1		2.88	11.20
1.5		2.95	13.90
2		2.62	1.16
0	28	3.09	0
0.5		3.25	5.18
1		3.34	8.09
1.5		3.41	10.36
2		3.21	3.88
0	90	3.35	0
0.5		3.47	3.58
1		3.55	5.97
1.5		3.67	9.55
2		3.42	2.09

Table 5: Split tensile strength of HFRC

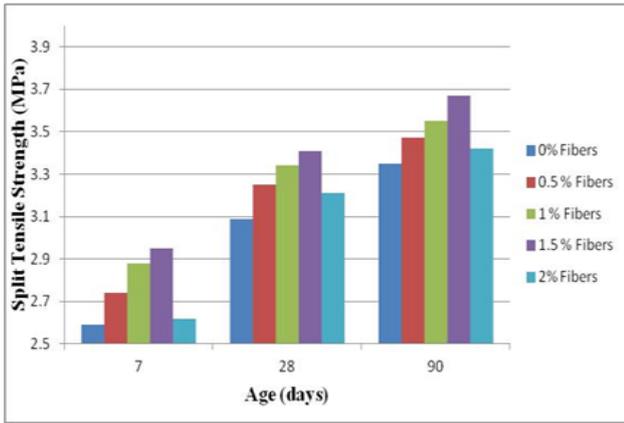


Fig. 4: Split Tensile Strength (MPa) vs Age

It is to be noted that the significant improvement in split tensile strength is mainly due to the addition of fibers in concrete. From the results it is concluded that the fibers blending will enhance the initial crack stress, ultimate strength and toughness after cracking. Thus hybridization results in bridging of both micro cracks and macro cracks in the different stages by choosing an appropriate fiber to the concrete mix gives the best tensile strength results as compare to conventional concrete

However, when the percentage fibers were increased to 2% a drastic fall in tensile strength was evidenced irrespective of the time of curing. The tensile strength values of all the mixes with 2% addition of fibers were found to be 2.62 MPa, 3.21 MPa and 3.42 MPa respectively after 7, 28 and 90 days of curing.

E. Impact Strength

Table 6 and Graph:3. show the impact strength results of HFRC mixes (0%, 0.5%, 1%, 1.5% and 2%) at 28 days of curing period.

% f Fibers	Firses visible crack in no.of blows	Final failure in no.of blows
0	4	15
0.5	7	29
1	9	48
1.5	16	61
2	17	64

Table 6: Impact strength of HFRC

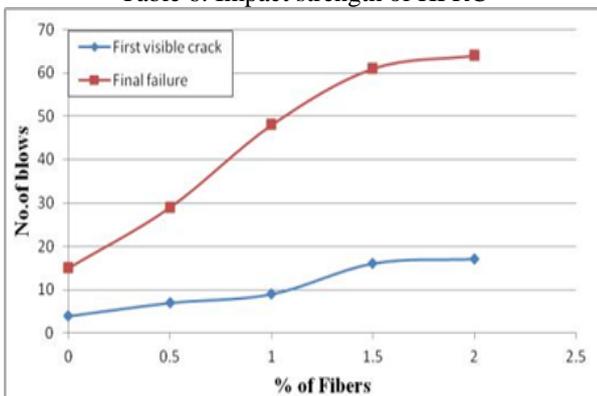


Fig. 5: % of fibers Vs No. of Blows

From the Table 6 and Graph:3, It is clear that the number of blows required for the failure of impact specimen had been increasing when the percentage of fibers in concrete mix is increased. The number of blows required for visible crack for 0.5% is 7 and for failure is 29. As the fiber

percentage is increased to 1% ,1.5% and 2% the number of blows required to initial crack and also final failure are noted as 9,16,17 and also 48,61,64 respectively. Thus from the above results it resembles that as fiber percentage in concrete mix increases the impact resistance of concrete increases.

F. Sorptivity Test

Table 7 and Graph 4 shows the sorptivity results of HFRC mixes (0%, 0.5%, 1%, 1.5% and 2%) at 45 days of curing period.

% Fibers	Dry weight (gm)	Wet weight (gm)	Sorptivity (10^{-5} mm/min $^{0.5}$)
0	8108	8112	3.24
0.5	9036	9044	6.49
1.0	8624	8636	9.73
1.5	8642	8655	10.54
2	8672	8687	12.17

Table 7: Sorptivity test results of HFRC

From the Table 7 and Fig. 6, it is clear that the sorptivity values have been increasing from 0% to 2%. At 0.5% fiber percentage the sorptivity value is 3.24. As the fiber percentage is increased from 0.5%, 1%, 1.5% and 2% the values of sorptivity are 6.49, 9.73, 10.54 and 12.17 respectively. Finally I concluded that the percentage of fibers influence the sorptivity of HFRC directly. Here, the sorptivity values are in 10^{-5} mm/min 0 .

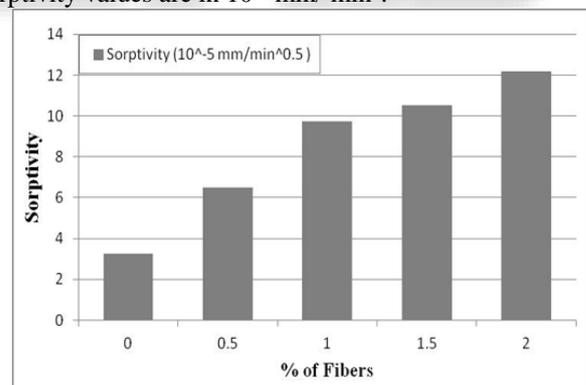


Fig. 6:

VI. CONCLUSIONS

Based on the investigation, the following conclusions have been drawn.

- 1) As the fibers content in the mix increases, there is a decrement in the workability of the concrete. Bleeding property also reduced due to the addition of fibers.
- 2) There was a significant increase in compressive strength and split tensile strength with the increase in percentage of fibers from 0% to 1.5% in all curing periods.

- 3) When the percentage of fibers was increased to 2% a drastic fall in compressive strength and split tensile strength were evidenced.
 - 4) The significant improvement in mechanical properties up to 1.5% fibers addition in concrete mixes is mainly due to nullifying the micro and macro cracks developed in the HFRC.
 - 5) The impact strength and sorptivity of HFRC have been improved, when the fibers are added in the mix. It resembles that as fiber percentage in concrete mix increases the impact resistance and sorptivity of concrete will be increases.
- [13] Wakchaure M. R, Rajebhosale S. H, Satpute M. B, Kandekar S. B, Comparison of compressive strength and flexural shear strength for hybrid fiber reinforced concret with controlled concrete, International Journal of Engineering and Technical Research, 2(2014) 172-175.

REFERENCES

- [1] Chetna M, Darshana R, Concept of green concrete using construction demolished waste as recycled coarse aggregate, International Journal of Engineering Trends and Technology ,4 (2013) 3160-65.
- [2] Sreenivasulu C, Guru Jawahar J, Vijaya Sekhar Reddy M and Pavan Kumar D, Effect of fine aggregate blending on short-term mechanical properties of geopolymer concrete, Asian Journal Of Civil Engineering (Building and Housing),17(2016) 537-550.
- [3] Vijai K, Kumutha R, Vishnuram B G. Effect of inclusion of steel fibres on the properties of geopolymer concrete composites, Asian Journal of Civil engineering, 13(2012) 377-85.
- [4] Khaloo A.R, Sharifian M, Experimental investigation of low to highstrength steel fiber reinforced lightweight concrete under pure torsion, Asian Journal Of Civil Engineering (Building and Housing), 6(2005) 533-547.
- [5] Shende A.M, Pande A.M, Gulfam Pathan M, Experimental study on steel fiber reinforced concrete for M-40 grade, International Refereed Journal Engineering and Science,1 (2012) 043-048.
- [6] Prasad M.L.V, Rathish Kumar P, Strength studies on glass fiber reinforced recycled aggregate concrete, Asian Journal of Civil Engineering (Building and Housing), 8(2007) 677-690.
- [7] Oucief H, Habita M.F, Redjel B, Hybrid fiber reinforced self-compacting concrete: hardened properties, International Journal of Civil Engineerng, 8(2006) 77-85.
- [8] Ghorpade Vaishali G, Sudarsana Rao H, Strength and permeability characteristics of fiber reinforced high performance concrete with recycled aggregates, Asian Journal of Civil Engineering (Building and Housing), 13(2012) 55-77.
- [9] Sreenivasa Rao A, Appa Rao G, Fracture mechanics of fiber reinforced concrete: An overview International Journal Engineering Innovation & Research, 3(2014) 517-524.
- [10] Miloud B, Permeability and porosity characteristics of steel fiber reinforced concrete, Asian Journal of Civil Engineering (Building and Housing), 6(2005) 317-330.
- [11] Ranjith Kumar R, Vennila A, Southamirajan S , Experimental investigation on hybrid fiber reinforced concrete, International Journal of Emerging Trends in Engineering and Development, 3(2013) 39-45.
- [12] Chandra mouli K, Srinivasa Rao P, Pannirselvam N, Seshadri Sekhar T, Sravana P, Strength properties of glass fibre concrete, ARPN Journal of Engineering and Applied Sciences, 5(2010) 1-6.